

• English

Lamination Guide

# SentryGlas<sup>®</sup> Xtra<sup>®</sup>

**kuraray**

**SentryGlas<sup>®</sup>**

## Introduction

# Interlayer strength, depth and capabilities

Delivering your window into the world of advanced interlayers for laminated safety glass, Kuraray's Advanced Interlayer Solutions Division (AIS) is underpinned by decades of innovation, application knowledge, domain experience and market success.

**OUR ADVANCED INTERLAYER PORTFOLIO** – comprising Trosifol® PVB and SentryGlas® ionoplast interlayers – has continually revolutionized aesthetic, structural and functional glass design, fabrication and installation in the architectural and automotive/transportation segments.

Designed to benefit consumers, society and industry, our products are advancing the functionality of glass, while our engineers and consultants are setting new application benchmarks by collaborating on solutions that both sustain and inspire.

We are committed to helping you transform your mindset and take your applications to the next level – aesthetically, functionally and structurally. Enjoy greater design freedom and give your glazing strength, clarity, character and purpose with solutions that cover safety, security, sound insulation, UV/solar/energy management, color and print.





Steve Jobs Theater Pavilion, Cupertino, USA

Steve Jobs Theater Pavilion, Cupertino, USA

**OUR DIVERSE PRODUCT RANGE,** the broadest on the global market and our domain expertise create strength; and we channel this strength into helping you succeed. We strive to be your strongest ally and supporter and will help you navigate and conquer the ever-changing demands of the global glass industry. Worldwide production, R&D and support, means we are always by your side... no matter where you are.



Photo: © One Works

Venice Airport, Italy

# Contents

|  |       |
|--|-------|
| ➔ Product offering SentryGlas Xtra®                          | 05-06 |
| Packaging  | 07    |
| Handling & storage   | 07-10 |
| Cutting & trimming   | 11    |
| Cleaning   | 12    |
| Glass washing  | 12    |
| Roller process   | 12-14 |
| Vacuum bag / Ring Process                                    | 15    |
| Autoclaving  | 16-18 |
| Processing thin 0.76 / 0.89 mm (35 / 35 mil) sheeting        | 19    |
| SentryGlas Xtra® interlayer multi-ply sheet lamination       | 20    |
| Laminating with point fixated glass (holes)                  | 21-23 |
| Vacuum bagging   | 22    |
| Compatibility of SentryGlas Xtra® with coated glass or frits | 23    |
| Non-autoclave processing                                     | 24    |
| Quality assurance testing                                    | 24    |
| Performance monitoring testing                               | 24    |
| Troubleshooting guide  | 25    |
| Additional information                                       | 25    |
| Tools & Apps   | 26    |
| Contact  | 27    |



➔ King Power Mahanakhon, Bangkok, Thailand

# Product offering

## SentryGlas Xtra®

The table below lists all of the current Kuraray product offering for SentryGlas Xtra® ionoplast interlayers. The interlayer is made in many different thicknesses and widths. It is packaged both in sheets and in roll form.

### SentryGlas Xtra® – dimensions for products on rolls


| Type             | Thickness<br>[mm] [mil] |    | Color | Roll widths<br>[mm]     | Roll widths<br>[in] | Roll lengths<br>[m] [ft] |     |
|------------------|-------------------------|----|-------|-------------------------|---------------------|--------------------------|-----|
| SentryGlas Xtra® | 0.76                    | 30 | Clear | 1050-3300* <sup>1</sup> | 41-130              | 250                      | 820 |
| SentryGlas Xtra® | 0.76                    | 30 | Clear | 1050-3300* <sup>1</sup> | 41-130              | 60                       | 197 |
| SentryGlas Xtra® | 0.89                    | 35 | Clear | 1220-3300* <sup>1</sup> | 48-130              | 200                      | 656 |
| SentryGlas Xtra® | 0.89                    | 35 | Clear | 1530-3300* <sup>1</sup> | 60-130              | 50                       | 164 |
| SentryGlas Xtra® | 1.52                    | 60 | Clear | 1050-3300* <sup>1</sup> | 41-130              | 130                      | 430 |

**TAB 1** • \*<sup>1</sup> Only available in standard width. Other sizes available on request with minimum order quantities and binding purchase commitment.

### SentryGlas Xtra® – dimensions for sheet products

| Type             | Thickness<br>[mm] [mil] |     | Sheet widths<br>[mm] | Sheet widths<br>[in] | Sheet lengths<br>[m] [ft] |    |
|------------------|-------------------------|-----|----------------------|----------------------|---------------------------|----|
| SentryGlas Xtra® | 0.89                    | 35  | 610-2160*            | 24-85*               | 6                         | 19 |
| SentryGlas Xtra® | 1.52                    | 60  | 610-2160*            | 24-85*               | 6                         | 19 |
| SentryGlas Xtra® | 2.28                    | 90  | 610-2160*            | 24-85*               | 6                         | 19 |
| SentryGlas Xtra® | 2.53                    | 100 | 610-2160*            | 24-85*               | 6                         | 19 |

**TAB 2** • \* Oversize shipment possible up to 2500 mm / 99 inches

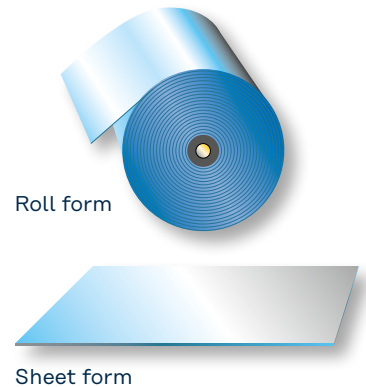

SentryGlas Xtra®\* – physical properties

| Type             | Adhesion | Film thickness |       | Color | Light transmittance*1 [%] | UV transmittance*1 [%] | Solar absorption*1 [%] |
|------------------|----------|----------------|-------|-------|---------------------------|------------------------|------------------------|
|                  |          | [mm]           | [mil] |       |                           |                        |                        |
| SentryGlas Xtra® | high     | 0.76           | 30    | Clear | 88                        | < 1                    | 16                     |
| SentryGlas Xtra® | high     | 0.89           | 35    | Clear | 88                        | < 1                    | 20                     |
| SentryGlas Xtra® | high     | 1.52           | 60    | Clear | 88                        | < 1                    | 21                     |
| SentryGlas Xtra® | high     | 2.28           | 90    | Clear | 88                        | < 1                    | 22                     |
| SentryGlas Xtra® | high     | 2.53           | 100   | Clear | 88                        | < 1                    | 22                     |

**TAB 3**
\* LSG with 2 x 4 mm Floatglass according EN 410/ISO 9050
\*1 Values calculated using Lawrence Berkeley National Laboratory Optics5 and Windows5 software.
Not all products are available in all regions.



Photo: © ymgerman/shutterstock.com

# Packaging

Kuraray offers SentryGlas Xtra® interlayer both as sheets that are packed horizontally on a pallet (Figure 1) and in roll form (Figure 2). Both come hermetically sealed in foil

bags to protect the sheets from moisture and contamination. The foil package is encased in cardboard to prevent damage that can occur during shipping.



FIG 1 • SentryGlas Xtra® interlayer sheet package on pallet



FIG 2 • SentryGlas Xtra® interlayer roll package on pallet


# Handling & Storage

*Unopened* sheeting and rolls require no temperature control for storage because SentryGlas Xtra® does not “block” like PVB interlayer does. SentryGlas Xtra® sheeting maintains its properties and overall quality consistency for many years under moisture proof storage conditions. Since moisture pick up over time can lead to deterioration in glass adhesion performance, it is recommended that SentryGlas Xtra® sheets or rolls in unopened packages be tested for moisture level and post lamination adhesion performance if the product is stored beyond three years from its original manufacturing date.


SentryGlas Xtra® will however, absorb water when opened packages and rolls are exposed to ambient conditions. *While the water absorption rate is very slow compared to PVB, water absorption of SentryGlas Xtra® will adversely affect adhesion.* It is recommended that the interlayer not be used if the moisture exceeds 0.2 % (when measured by Karl Fischer titration).

Figure 3 is the graph showing water absorption rate for 90-mil sheeting exposed to 3 different relative humidity levels. Upon opening, all packages or rolls of SentryGlas Xtra® need to be properly resealed.


## SentryGlas Xtra® moisture uptake at 27% RH

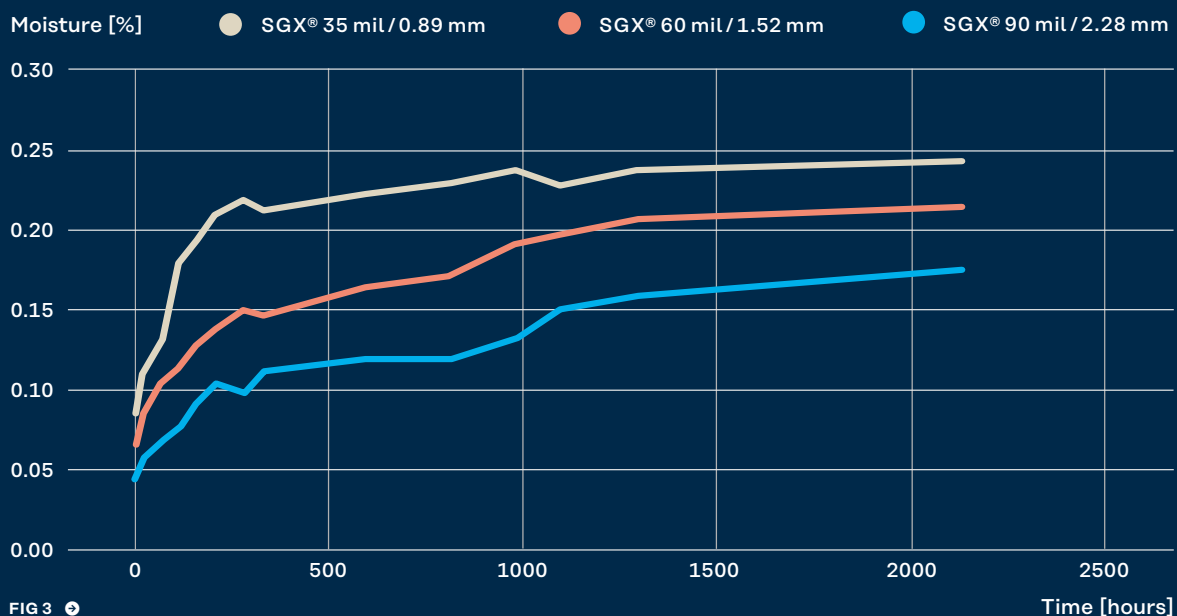

## SentryGlas Xtra® moisture uptake at 50% RH

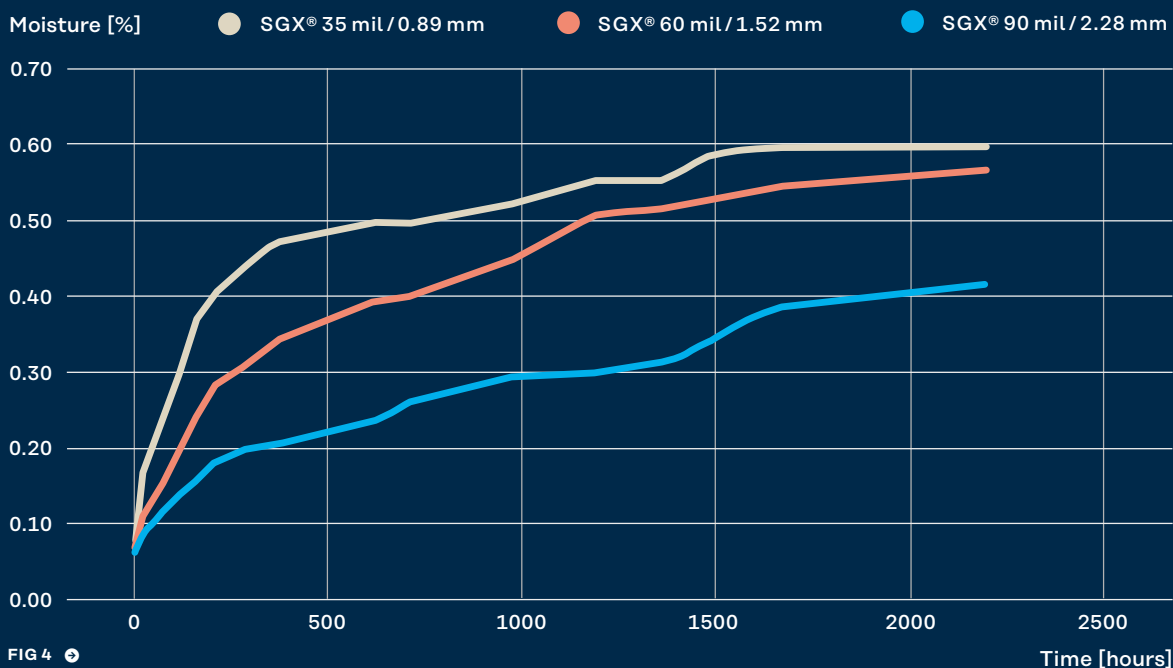

## SentryGlas Xtra® moisture uptake at 75% RH

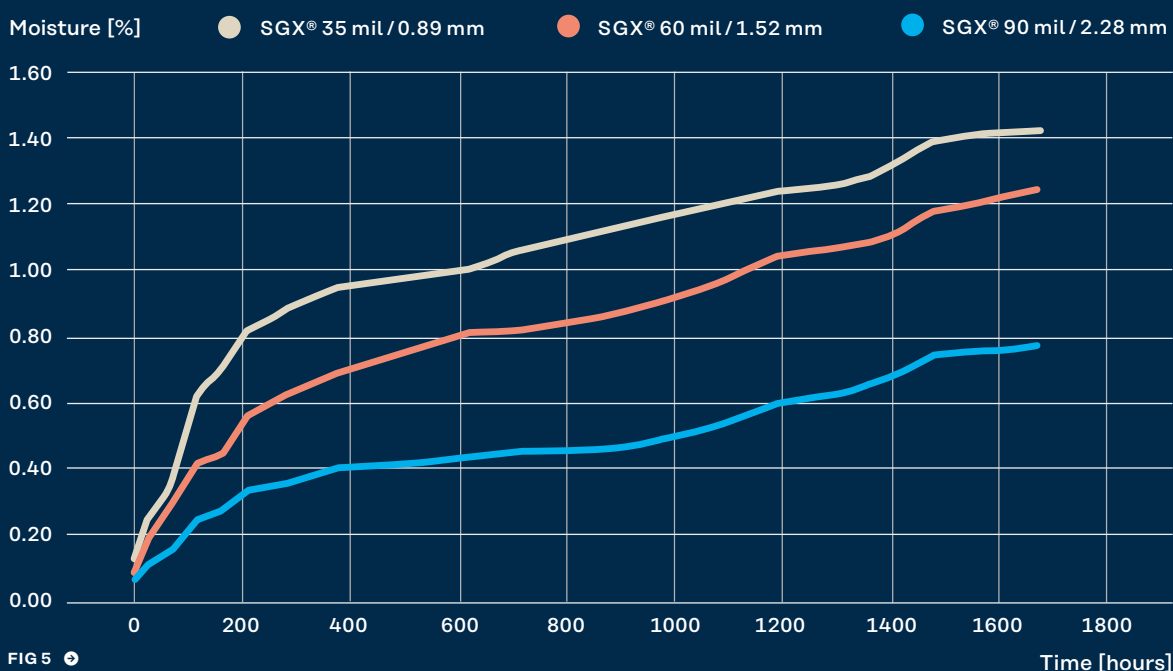

The recommended procedures for storing and handling of SentryGlas Xtra® differ for sheets versus rolls. SentryGlas Xtra® sheets are packaged horizontally in stacks that are wrapped in a moisture resistant foil packaging film and shipped on pallets. Cardboard is used to both support the package and minimize sheet deformation. The packages should be stored so that the sheets do not become deformed which could impact lamination. Heavy loads

placed on SentryGlas Xtra® sheet stacks can deform the sheets through the packaging foil. The protective cardboard top layer should always be as the barrier between stacks. Product pallets can be stacked on one another, up to 5 pallets, provided that the stack top surfaces are supported with the cardboard flat to prevent pallet runner boards from imprinting product sheets through the foil packaging.

The use of overhead racks (see Figure 4) is a good alternative to stacking pallets on the floor since it minimizes sheet deformation while reducing the overall storage footprint. The recommended procedure for opening the foil packaging, removing sheets and then resealing it is:

1. Use a utility knife or scissors to trim off the excess foil just inside the heat sealed line (see red arrow in figure 5) leaving as much excess foil as possible for resealing.
2. Using lint free gloves, remove the top sheet by lightly “wafting” it once prior to pulling it out of the bag. This process forces air underneath the sheet allowing for easy removal.
3. Close the bag and fold over the excess foil. Seal the entire seam to the bulk of the package using either a medium tack tape (see Figure 6) or a heat gun.

Resealed packages can be stored in either a humidity-controlled environment or under ambient conditions. If there is a concern regarding the moisture level of an opened package please contact your Kuraray sales or technical representative prior to use.



FIG 6 • Overhead storage racks



FIG 7 • Heat sealed line in foil packaging



FIG 8 • SentryGlas Xtra® interlayer package – properly resealed with tape

## RECOMMENDATIONS FOR STORAGE CONDITIONS OF SENTRYGLAS XTRA® ROLLS OR SHEETS:

- **Originally sealed:**
  - Roll or sheet can be stored in temperatures not exceeding 30°C (86°F)
- **Opened packaging:**
  - **If roll or sheet is directly used:**  
In an air-conditioned room at 18-20°C (64-68°F) and 25-30% RLH (same conditions as PVB)
  - **If the material is stored for longer time:**  
In an air-conditioned room at 18-20°C (64-68°F) and ≤10% RLH



FIG 9 • Horizontal roll sling



FIG 10 • Horizontal roll lift

## RECOMMENDED PROCEDURE FOR STORING AND HANDLING THE ROLLS

1. Always store and handle a SentryGlas® Xtra® interlayer roll horizontally not vertically.
2. The roll crates can be double stacked.
3. Open the crate and then using straps (see figure 7) lift the roll and place it onto a cradle (please note when using straps ensure the roll is properly balanced). Remove the endplates and core plugs.
4. Using either a horizontal roll lift (see figure 8) or another similar device suspend the roll off the cradle. Then carefully open the moisture proof packaging by either:
  - a. Trimming open one end of the foil and sliding the foil off over the roll or
  - b. Cutting the foil near the seal to retain as much original packaging material as possible and removing it.
5. Retain the moisture resistant bag for future use.
6. Place the SentryGlas Xtra® interlayer roll into the desired carousel
7. Cut the sheeting to the desired size using a Rosenthal or similar type sheeter and stack the sheets with the edge curl face down.
8. After sheeting is complete remove the roll from the carousel. Cover the SentryGlas® Xtra interlayer roll with the original moisture resistant packaging. Collapse the moisture resistant packaging around the roll to remove as much air as possible. Seal any opening in bag with tape.
9. Insert the excess foil from each end into the core and re-insert the end plates and core plugs.
10. Inspect the roll for holes or tears in the foil packaging.
11. Place sealed SentryGlas Xtra® interlayer roll in storage.

# Cutting & Trimming

The SentryGlas Xtra® interlayer sheeting needs to be properly sized prior to lay-up if not purchased cut-to-size. The recommended methods for sizing involve using a shear cutter or an automated table cutter, since these minimize the cutting debris compared to other methods such as sawing. Since the sheeting has excellent dimensional stability, it can be cut to nominal glass dimensions and post-assembly trimming may not be required.

## SIX TYPICAL METHODS USED TO CUT SENTRYGLAS XTRA®

1. Shear type guillotine
2. Static automated table cutters (e. g. Eastman)
3. Utility knife: Score → Fold over → Tear
4. Die cut
5. Machine score then snap out
6. Size with a Rosenthal or similar sheeter 0.76 mm / 35 mil sheeting only)

For initial trials, the most straightforward and economical method to cut SentryGlas Xtra® is to use a utility knife. The recommended procedure for this method is detailed below.

1. Use a template to ensure the interlayer is cut to the proper dimensions. If laminating a curved or irregular shape surface (like a sidelite) an unbent sidelite or glass lite works very well. Trace the template with a utility knife or a razor cutter leaving a light score mark (Figure 9).
2. Fold the sheet along the entire scored perimeter.
3. Tear/snap-out along the scored boundary (figure 10).
4. Remove any debris using a Tek Nek roller or a lintless wipe.

The use of a saw is not a recommended method for sizing the interlayer unless the cuts can be made with little or no edge debris.



FIG 9 • Cutting SentryGlas Xtra®: Score pattern using a utility knife

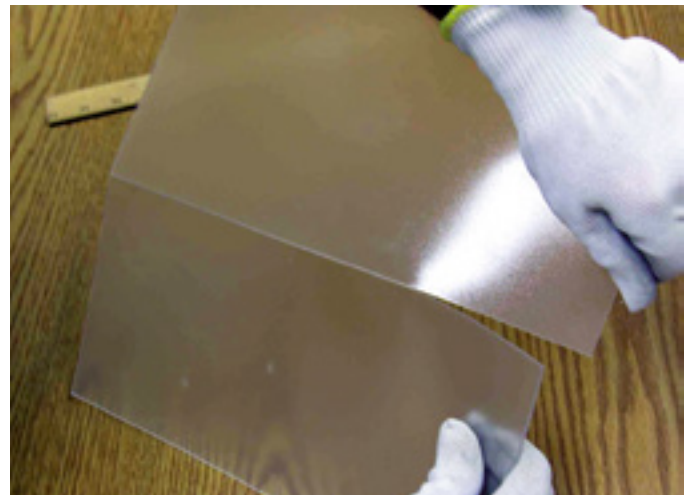


FIG 10 • Cutting SentryGlas Xtra®: Tear along scored pattern

# Cleaning

SentryGlas Xtra® interlayer sheets are delivered clean but they are electrostatic. This can result in surface contamination if not cleaned during lay-up. Prior to assembly a final cleaning step is recommended especially if the sheets are cut or trimmed. Cleaning can be done by using one of the following methods:

- **Contact tacky roller (e.g. Tek Nek or SDI (see Figure 11)).** Ensure that when purchasing the tacky rollers and cleaning pads that they are silicone free.
- **Ionized air**
- **Lintless wipe**

Use of a glass washer for cleaning SentryGlas Xtra® is not recommended. If the interlayer is cut using a saw (not recommended), it may be necessary to remove sheet shavings using a glass washer. If a glass washer is necessary, the following details are suggested:

- **Do not use detergent.**
- **Use de-ionized (DI) water.**
- **Ensure water temperature is kept below 100 °F (38 °C).** The use of hot water increases the potential for sheets to get caught in the glass washer.

## Glass washing

The recommended method for cleaning the glass is to wash with detergent and rinse the lites with de-mineralized or de-ionized water. The use of unfiltered (hard) water or simple ion exchange (soft) water to clean the glass is not recommended since it may lower the laminate's adhesion. Excellent results have been obtained using various commercial grade detergents such as Basic H; however, the effect of specific detergents on the adhesion of SentryGlas Xtra® has not been detailed. Each detergent should be evaluated prior to routine production. Good adhesion can also be obtained without the use of detergent but the temperature of the wash water should be > 54 °C /130°F to ensure the best results.



FIG 11 • Cleaning SentryGlas® with contact roller

## Roller process

Glass lamination requires a de-airing step to remove the air at the glass/interlayer interface. De-airing can be accomplished with either a roller press (single or double nip) or using a vacuum process. The embossed surface of the SentryGlas Xtra® facilitates the de-airing process before adherence to the glass occurs. While SentryGlas Xtra® interlayer in sheet form will lay flat on the glass at assembly there may be some waviness in the rolled sheet at lay-up (see figure 12). While the undulations in the sheeting may increase when stacking multiple sheets (see figure 13) the waviness should not impact final laminate quality if processed per the recommended nip roll guidelines (see figure 14).

Due to variations in equipment, the optimum temperatures and nip roll settings can be different for each laminator. Line speeds will depend on the temperature of the laminates during the process and the laminate appearance upon exiting the furnace. The laminate temperature will depend on many factors such as glass thickness, glass coating, oven type, and oven settings. Line conditions, such as power output and wavelength, can vary greatly for an IR furnace compared to a convective furnace. Although wavelength dependent, SentryGlas Xtra® interlayer absorbs IR radiation much better than glass (see Figure 15) thus line speeds are faster than processing using a convective line. The following guidelines are recommended for the initial lamination of SentryGlas Xtra®.



FIG 13 → Prepress interlayer waviness multiple sheets

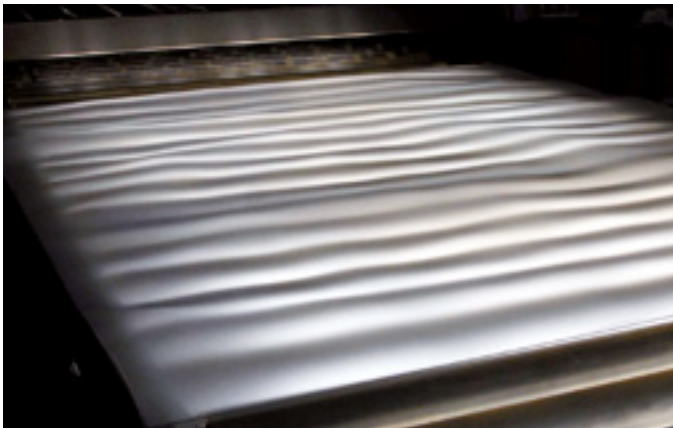


FIG 12 → Prepress interlayer waviness



FIG 14 → Nip roll process

## SentryGlas Xtra® total solar transmission

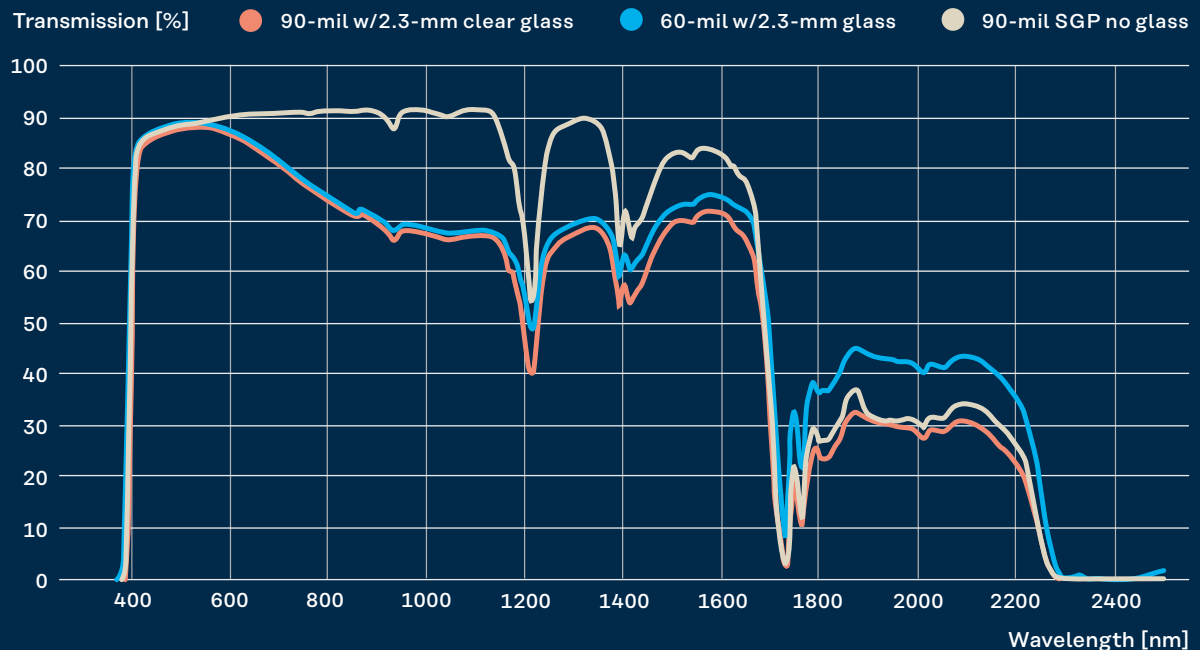


FIG 15 →

## ADJUSTMENTS TO THESE PARAMETERS MAY BE NEEDED TO ATTAIN THE HIGHEST QUALITY PRE-PRESS:

- Laminate temperature exiting last roller:  $63 \pm 8^\circ\text{C}$  ( $145 \pm 15^\circ\text{F}$ ). Speed should be set to obtain the desired last roller exit temperature, which is based on prepress appearance. The optimum prepress should have a well-defined edge seal (clear along the entire perimeter).
- The prepress appearance for laminates made with IR nip roll lines should have a minimum of 19 mm (0.75") clear edge seal around the entire perimeter (2 cm). While the outside of edge of the laminate should be clear the interior will likely still be hazy (translucent) after prepressing due to residual surface pattern (see Figure 16). The optimum prepress temperature will be at the lower end of the recommended range.
- Convective furnaces tend to operate from the middle to upper range for the recommended glass temperature. The overall appearance will be mostly clear (see Figure 17).
- If a line of trapped air bubbles can be seen at the trailing edge of the prepress made on either a convective or IR line the laminate was most likely made at too high of a temperature resulting in a premature edge seal (see Figure 18).
- Roller pressure and opening:
  - 3 mm (0.125") less than total laminate thickness for annealed glass.
  - Decreasing the nip gap maybe necessary if using heat strengthened glass that contains roller wave.
  - Air pressure to the nip rolls should be 5 bar (75 psi) or greater.
  - Open up first nips if any glass slippage occurs



FIG 16 • Proper edge seal IR



FIG 17 • Convective line prepress appearance



FIG 18 • Trapped air in trailing edge

# Vacuum bag / Ring process

Although using a vacuum ring or vacuum bag process is slower and more labor intensive than nip rolling it typically has better post autoclaving yields with respect to air related defects. It is the recommended process for making very large tempered laminates or multi-laminates. Disposable or re-usable systems can be used for vacuum bagging. Disposable types are hand constructed to the dimension of the laminate (Figure 19). It is necessary to use a porous strip along the edge of the laminate inside the plastic bag to allow complete de-airing of the laminate. To keep the edge of the interlayer smooth for open edge applications a gas permeable tape can be inserted around the perimeter of the laminate between the interlayer and the porous strip. If sticking occurs between the strip and the interlayer use of a perforated release film between the two is recommended. Any material used in vacuum processing a laminate with heat should be rated for this application.

Re-usable systems include silicone rubber envelope bags (see figure 20) and clamshell assemblies (see figure 21). The cold vacuum time should be a minimum of 10 minutes. The hot vacuum temperature should be set based on the prepress appearance of the laminate. However, if desired, laminates can be made without the prepress operation by applying vacuum directly during the autoclave cycle, thus reducing handling and cycle time.

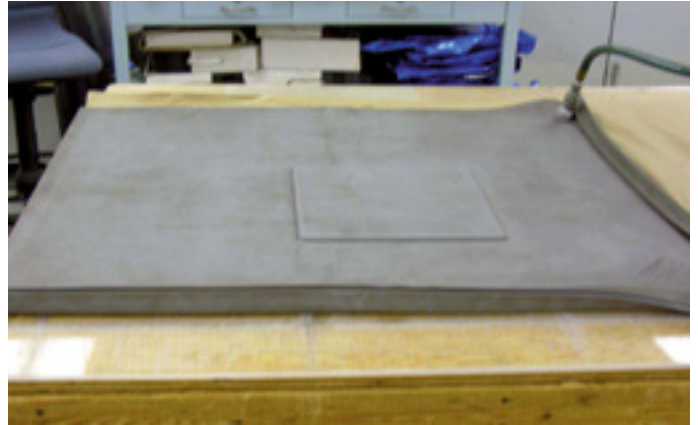


FIG 20 • Silicone rubber envelope bag (reusable)

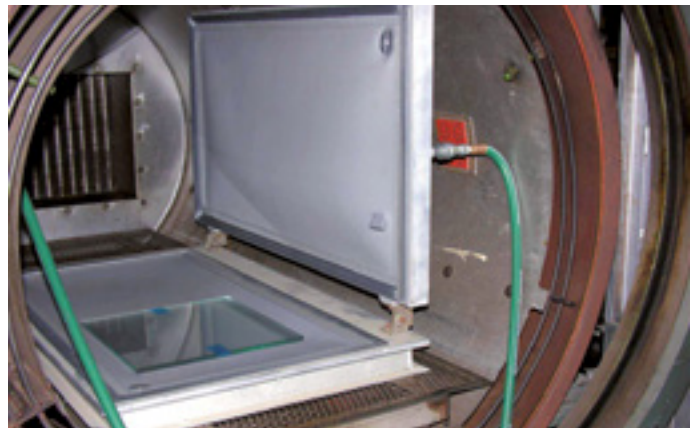


FIG 21 • Clamshell assembly (reusable)

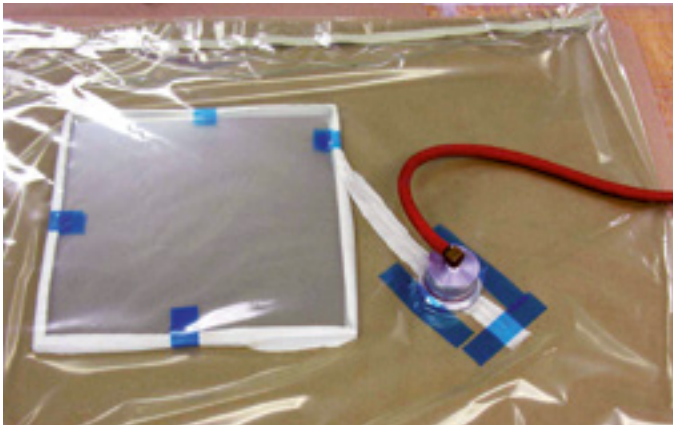


FIG 19 • Disposable vacuum bag

# Autoclaving

Control and monitoring of the autoclaving variables are essential to making quality laminates with SentryGlas Xtra® interlayer. Autoclave parameters including, prepress racking, soak time, soak temperature and cooling rate will influence both the optical and physical properties of the finished laminates. The laminates should be placed on the autoclave racks with  $\geq 19$  mm ( $\frac{3}{4}$ " ) spacing between pre-presses. Localized high stress areas need to be minimized by dispersing the load over a large area. Setting the laminate directly against the vertical rack supports should be avoided. Figure 22 is a photograph of laminates that have been racked improperly. Areas of uneven stresses (caused by placing laminates directly against some autoclave racks) can result in non-uniform interlayer thickness. This differential thickness can result in areas of high residual stress within the laminate and possible optical distortion. Figure 23 is a photograph taken with a polarized lens showing a laminate with optical distortion (iridescence), as a direct result of the autoclave racking conditions. Figure 24 is a photograph of the proper technique for racking pre-presses. The laminates are properly spaced with no airflow restrictions between the laminates.

Autoclaves vary greatly with respect to size, heating, cooling rate and overall efficiency. The recommended soak temperature range is 132 - 135 °C (270 - 275 °F). It is imperative that the autoclave soak time be long enough so that the interlayer reaches the desired temperature for the required time to ensure adequate adhesion. The minimum recommended hold time is 1 hour. Laminates that do not receive the required time can look good optically but can have low adhesion due to incomplete bonding between the glass and the interlayer. Thicker laminate constructions (> 16-mm) will require a longer soak time. Imbedding a thermocouple in the exact construction to be laminated will give the most precise time versus temperature relationship. The amount of haze in the final laminate is directly related to the autoclave cycle cooling rate. The faster the cooling rate the lower the haze. To ensure adequate cooling that the following recommendations apply:

To reduce the possibility of interlayer flow the maximum recommended autoclave temperature should not exceed 135 °C (275 °F). Figure 25 shows a typical autoclave profile used for SentryGlas Xtra® while Figure 26 shows one with a low pressure hold.



FIG 23 • Laminate showing optical distortion

1. Use a properly sized fan.
2. Use cold or cool water with sufficient flow to maximize heat exchange.
3. Flush the radiator on a routine basis. Laminates with high haze can be re-autoclaved to reduce the haze level provided the cooling rate meets The recommended requirements.

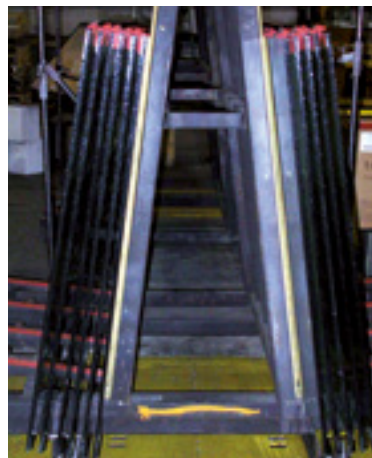


FIG 24  
• Properly racked laminates

## THE RECOMMENDED AUTOCLAVE PARAMETERS ARE:

- Temperature: 132 - 135 °C (270 - 275 °F)
- Pressure: 12-14 bar (180-200 psi). Note: Lower autoclave soak pressures can be used however, the susceptibility of air bubbles forming in a laminate may increase with decreasing pressure.
- Hold: 60 minutes (or greater depending upon laminate thickness, autoclave size, load and airflow).
- Cooling rate: A minimum of 1 °C / min (34 °F / min). The cooling rate is critical to minimizing haze formation in the laminates. It is recommended that the laminates be near ambient temperature prior to shutting off both the fan and the cooling water.

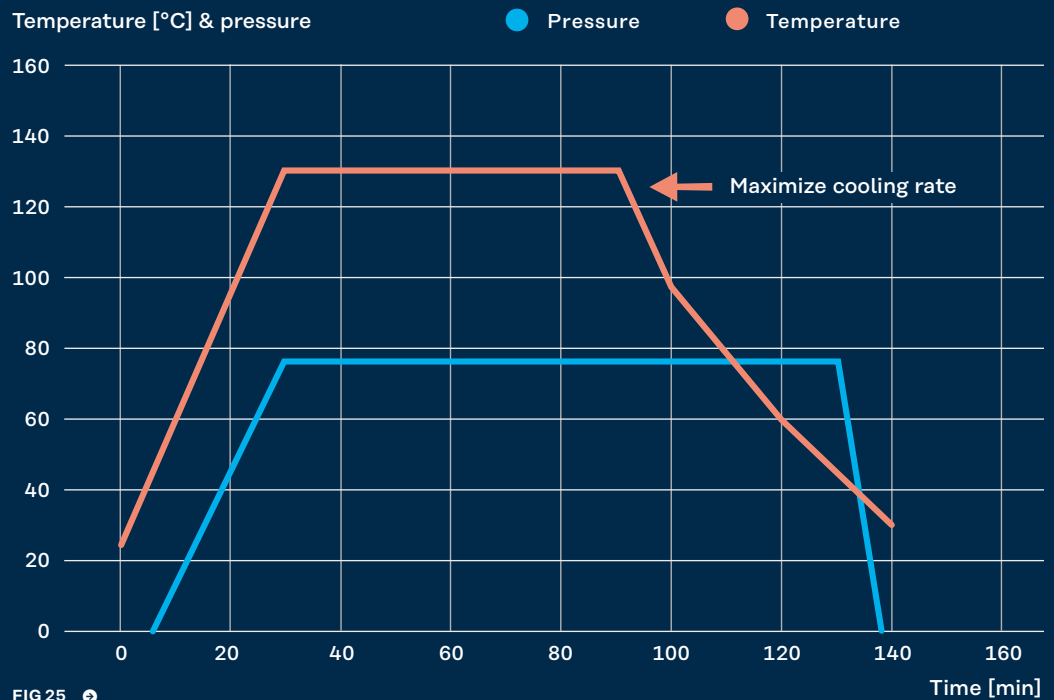


FIG 22 • Improperly racked laminates

## Temperature Metric/Imperial

| °C  | °F  |
|-----|-----|
| 160 | 320 |
| 140 | 284 |
| 120 | 248 |
| 100 | 212 |
| 80  | 176 |
| 60  | 140 |
| 40  | 104 |
| 20  | 68  |
| 0   | 32  |


## A. Basic SentryGlas Xtra® autoclave profile



## Pressure Metric/Imperial

| bar | psi |
|-----|-----|
| 16  | 232 |
| 14  | 203 |
| 12  | 174 |
| 10  | 145 |
| 8   | 116 |
| 6   | 87  |
| 4   | 58  |
| 2   | 29  |
| 0   | 0   |

## B. Alternative SentryGlas Xtra® autoclave cycle with low pressure step (in case cycle A is not sufficient)

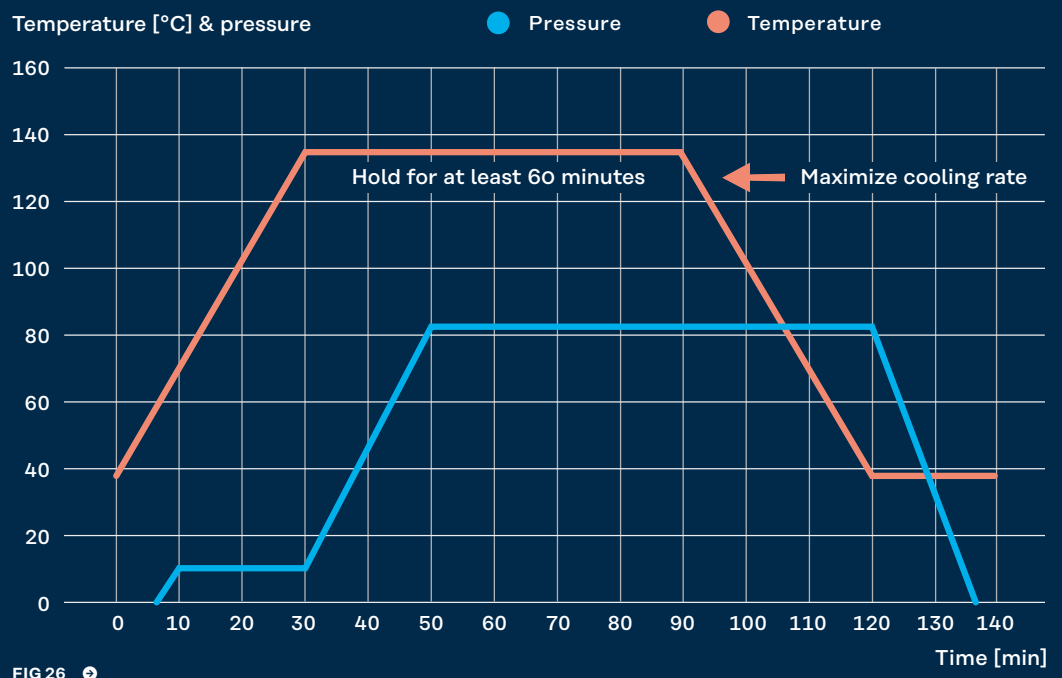

Temperature  
Metric/Imperial

| °C  | °F  |
|-----|-----|
| 160 | 320 |
| 140 | 284 |
| 120 | 248 |
| 100 | 212 |
| 80  | 176 |
| 60  | 140 |
| 40  | 104 |
| 20  | 68  |
| 0   | 32  |

C. Alternative SentryGlas Xtra® autoclave cycle with low pressure step and increased duration (in case cycle B is not sufficient)

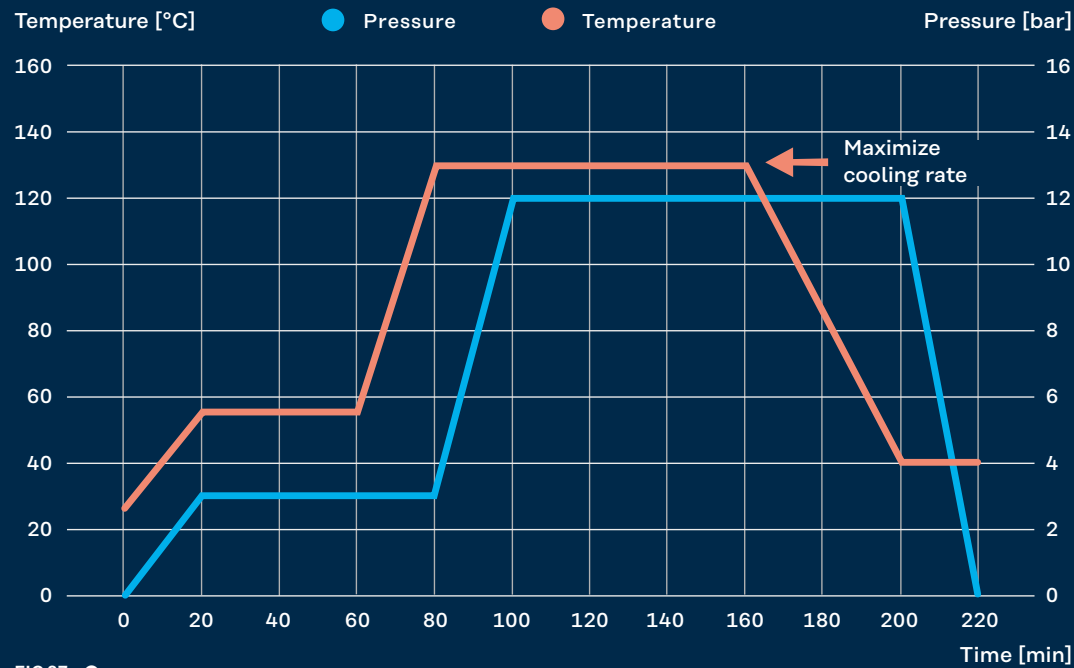


FIG 27

Pressure  
Metric/Imperial

| bar | psi |
|-----|-----|
| 16  | 232 |
| 14  | 203 |
| 12  | 174 |
| 10  | 145 |
| 8   | 116 |
| 6   | 87  |
| 4   | 58  |
| 2   | 29  |
| 0   | 0   |

D. Special autoclave cycle for SentryGlas Xtra® Multilaminates, big panes or intensive autoclave loadings


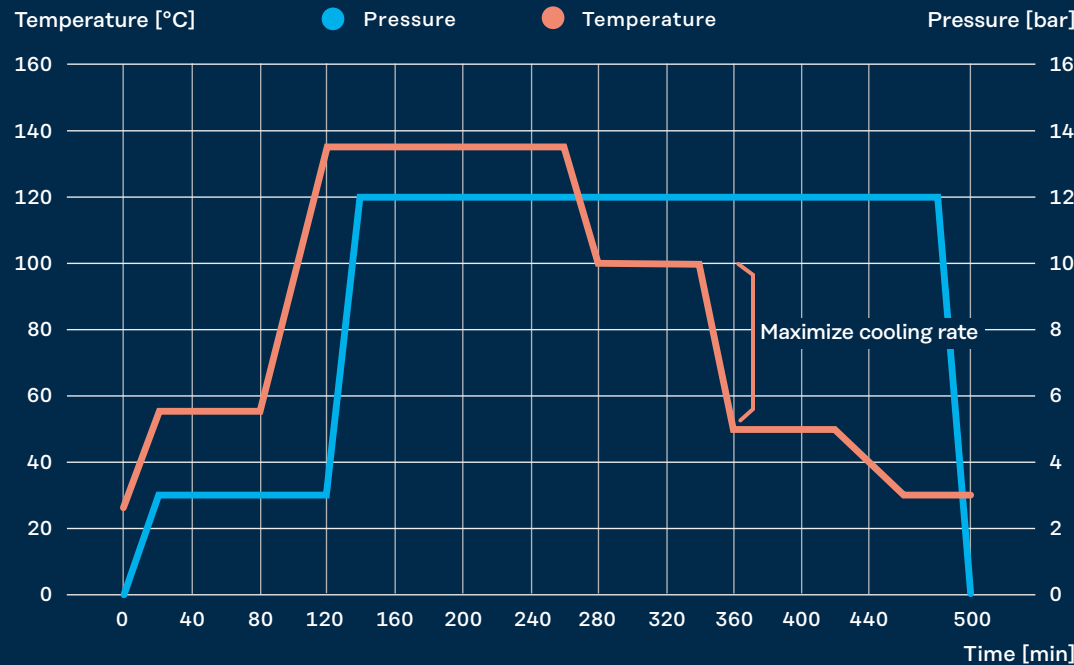


FIG 28

# Processing thin 0.76 / 0.89 mm (30 / 35 mil) sheeting

Thin 0.76 or 0.89 mm (30 or 35 mil) SentryGlas Xtra®, whether on rolls or in sheets, requires some slight differences in processing versus 1.52 and 2.28 mm (60 and 90 mil) SentryGlas Xtra®. Laminating with heat-strengthened or tempered glass requires the lites to have good flatness with minimal roller wave and edge kink.

## 35-mil SentryGlas Xtra® 5000 water absorption Vs % RH at RT

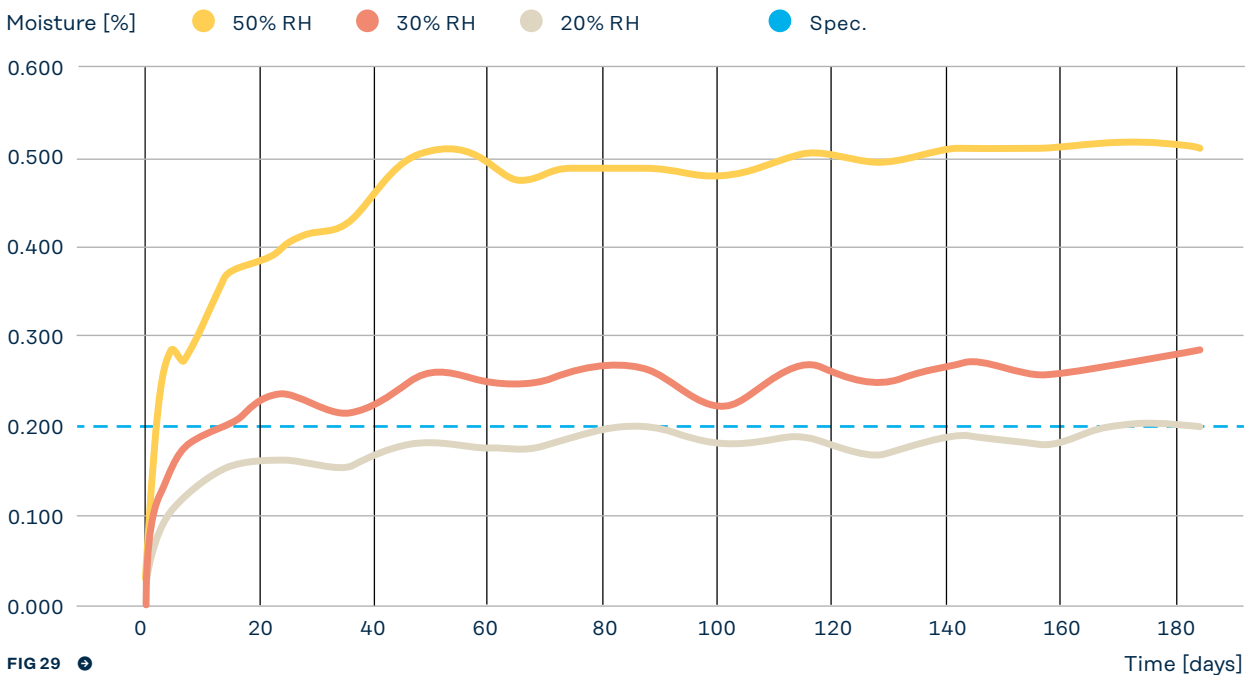

## THE FOLLOWING ARE RECOMMENDATIONS FOR PROCESSING THIN SENTRYGLAS XTRA® VERSUS THE THICKER CALIPERS:

- Storage & Handling:** Due to the increased surface area versus bulk thin sheeting absorbs moisture at a faster rate. Figure 29 is a graph showing moisture absorption versus time for 3 different (20, 30 and 50 %) relative humidity.
- Cutting & Trimming:** Unlike the thicker calipers 0.89 mm (35 mil) sheeting can be easily trimmed at lay-up with a hook knife. For lamination with heat-strengthened or tempered glass it is recommended that 1/8 – 1/4" excess material be left at lay-up. Any residual interlayer should be trimmed after autoclaving.
- Cleaning:** A tacky roller is the best method to clean the sheeting. Using a glass washer to clean the sheeting is not recommended since it will likely get caught in the washer's brushes.
- Heated Treated Glass:** Heat strengthened or tempered glass needs to be flat with minimal roller and edge kink.
- Roller Processing:** The prepress appearance of a nip rolled 0.76 or 0.89 mm (30 or 35 mil) laminate should be similar to a 2.28 mm (90 mil) laminate. However, due to the less mass a slightly higher line speed maybe required.
- Autoclaving:** same as the thicker calipers

# SentryGlas Xtra® interlayer multi-ply sheet lamination

Achieving the desired laminate strength or projectile resistant properties may require laminating 2 or more sheets of interlayer together between two lites of glass. While any multi-ply sheet laminate can be vacuum bagged the nip rolling process window is limited.

## NIP ROLL PROCESS

Laminating any two sheets of SentryGlas Xtra® together can readily be done using a standard nip roll process. Each sheet surface should be cleaned e.g. tacky rolled prior to lay-up to minimize contamination. Line speed should be set so that there is a well-defined clear edge seal without trapping air in the trailing edge of the prepress. Laminating more than 2 sheets together between 2 lites of glass can be successfully done provided the total interlayer thickness does not exceed 5 mm (200 mil). Nip rolling more than 2 sheets together when the total interlayer thickness exceeds 200 mil can result in:

1. The internal SentryGlas Xtra® interlayer interfaces not getting enough heat to create a sufficient prepress bond resulting in pressurized air breaking the seal during autoclaving (see Figure 30).
2. Trapped air between the glass and the outermost interlayer ply when the prepress temperature is increased to improve the prepress bond between the internal SentryGlas Xtra® interlayer interfaces.

In addition to the flatness of the glass, successfully laminating more than two 2.28 mm (90 mil) sheets SentryGlas Xtra® together is dependent upon the type of line (IR versus convective), the parameters selected to run the line and the uniformity of heating within the prepress ovens.



FIG 30 •

## VACUUM PROCESS

Vacuum lamination, if done correctly, will result in laminates without trapped air defects and is the preferred method for laminating more than 2 sheets of SentryGlas Xtra® together. The vacuum processing procedures remain the same regardless of the total interlayer thickness except for:

1. Cold de-airing time may need to be increased as the number of sheets increases. Since the required time is dependent upon process conditions (vacuum level, size of vacuum pumps, laminate size, etc.) it is recommended that optimum cold de-airing time be determined empirically.
2. As the size and thickness of both the interlayer and laminates increases the autoclave soak time should also increase proportionally.
3. To minimize haze ensure the laminate temperatures have cooled to below 100°F prior to shutting off the fan and the cooling water in the autoclave

Please consult your Kuraray technical representative if there are questions regarding lamination of SentryGlas Xtra®.

# Laminating with point fixated glass (holes)

SentryGlas Xtra® does work well for point fixated systems i.e., laminates with holes provided the laminates are made correctly. Nip rolling versus vacuum bag processing is dependent upon the size, thickness and total amount of glass and/or interlayer plies required.

## NIP ROLL

SentryGlas Xtra® interlayer with holes can be processed with high yields using a nip roll process without the use of clamps. In addition, success can be achieved by either removing the interlayer from the holes before or after autoclaving.

The most common problem for yield loss after autoclaving in point fixated laminates with SentryGlas Xtra® is trapped air adjacent to the holes (see figure 31).

This is most often caused not by trapping air in during prepressing but by pressurized air breaking the edge seal during autoclaving. Autoclave “blow-ins” occurs due to insufficient edge seal around the hole. A high amount of uniform haze (residual surface pattern) around the hole is a result of prepressing too cold (see figure 32).

This can be corrected by running the prepress at a lower line speed. Non-uniform prepress haze around the hole is typified by having areas around the perimeter that are both clear and hazy (see figure 33). This is more difficult to rectify since it can be related to lack of flatness in the glass or variable heating across the laminate. Figure 34 shows the desired appearance of a prepress with a clear edge seal around the entire perimeter of the hole.

Removing the interlayer from the hole can be done either after prepressing or after autoclaving. While there are a number of methods for doing this one of the quickest and easiest methods is using a core or hole bit to drill out the SentryGlas Xtra® (see figure 35). The drill bit diameter should be slightly less than the hole diameter to minimize contact with the glass.

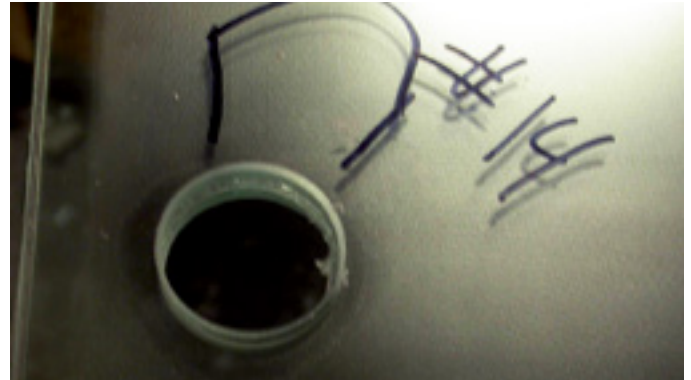


FIG 32 • Prepress too cold

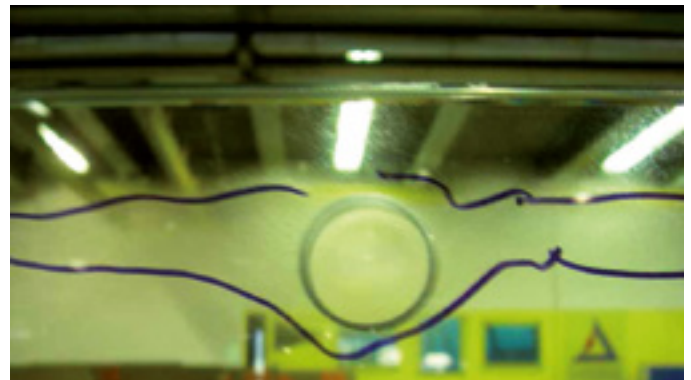


FIG 33 • Non-uniform prepress haze



FIG 34 • Proper prepress

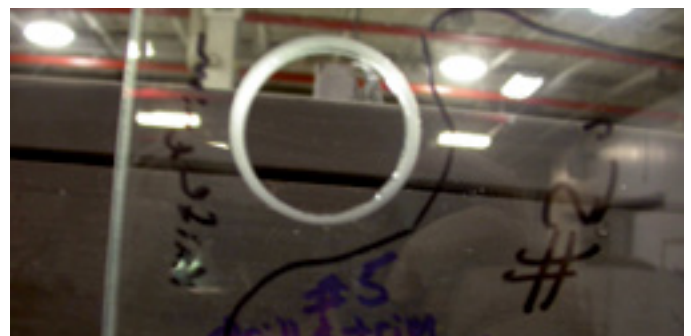


FIG 35 •

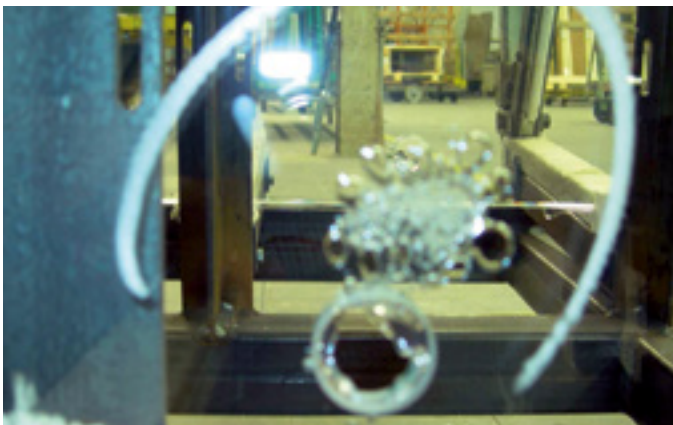


FIG 31 • Air near hole

Figure 34 shows a hole drilled after prepressing. Since the interlayer is hot coming directly from the oven it is best to allow some cooling to prevent sticking of the interlayer to the drill bit. After drilling, the remaining interlayer will need to be removed with either an exact blade or a hot knife (model ZTS 20 for example). The advantage of trimming the SentryGlas Xtra® interlayer flush after prepressing is that it is easier to remove since it is less stiff.

Good quality prepresses require **no clamps** during autoclaving. In addition, on precut holes there should be no flow of the interlayer from the hole during autoclaving thus no additional hole trimming should be required. Outward flow results in thinning of the interlayer which can result in delamination. To help prevent this ensure the soak temperature does not exceed 135 °C (275 °F) and there are no high stress areas pressing on the laminates. Minimizing distortion (roller wave, edge kink, etc.) is important. If there is flow of the SentryGlas Xtra® into the laminate leading to “short vinyl” around the hole perimeter this is typically a result of: a) excessive void space due to tempering distortion or b) thinning caused by pulling too hard on the soft interlayer during trimming. If this is observed post autoclaving hole drilling should rectify the problem.

The process for hole drilling and trimming before versus after autoclaving is the same. However, after autoclaving more force is required for trimming due to the increased stiffness.

## NIP ROLL PROCESS SUMMARY

1. Core drilling out the SentryGlas Xtra® works well either before or after autoclaving.
2. Core drilling after prepressing works best if the interlayer is allowed to cool partially before drilling.
3. Trimming the holes flush to the glass should be done using either an exact knife or a hot knife after core drilling is completed. Use of a torch is not recommended.
4. Clamps should not be used.
5. No flow of the interlayer out of the holes should occur during autoclaving thus inserting tape or other substances into the hole restrict flow of the interlayer should not be needed.
6. If the interlayer becomes recessed into the glass consider trimming after autoclaving.

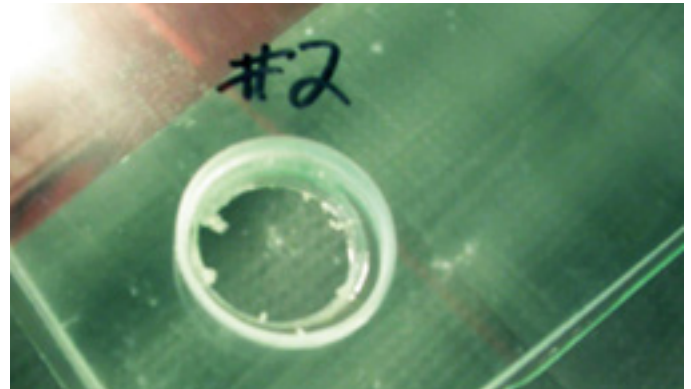


FIG 36 • Drilled hole after prepressing

# Vacuum bagging

For large thick tempered laminates or multi-ply glass panels vacuum bagging the laminates with SentryGlas Xtra® with holes is recommended to maximize yields. The vacuum bag process for laminates with holes is similar to that of standard laminates (no holes) except for the addition of a few extra steps.

It is recommended that in a vacuum process the interlayer not be removed the holes until after autoclaving to minimize flow into the laminate i.e. “suck-in”. The porous breather material to promote de-airing should be placed over each hole on the top and bottom of each prepress and taped in place (see figure 37) to prevent getting sucked into the hole. After autoclaving the interlayer can be removed from the holes using a core drill and a knife.

The remaining steps are the same as processing laminates without holes. An outline of the best practices of laminating SentryGlas Xtra® with holes in a vacuum bag process is listed below.



FIG 37 • Breather material over hole

## VACUUM BAG PROCESS OUTLINE

1. To minimize distortion and trapped air defects orient or nest heat treated the glass.
2. Depending on the size of the laminates, the amount of distortion in the glass and the thickness of the SentryGlas Xtra® the interlayer may need to be cut up to 5-mm oversized in length and width to allow for flow-in during autoclaving.
3. To maximize de-airing channels a porous breather material is needed along the entire glass/interlayer interface including holes. It is strongly suggested that the breather material be securely adhered to the outside of the glass using a high temperature rated tape. This will prevent the breather material from recessing into the laminate when under vacuum.
4. For large laminates maximizing the number of vacuum connections will improve de-airing efficiency.
5. To properly de-air the prepress it is important to maximize the vacuum level. It is recommended that the vacuum be  $\geq 28''$  Hg (93 % vacuum or 948 mbar).
6. Cold de-airing in the autoclave should be at least 60 minutes for large multi-ply laminates.
7. Autoclave soak time should be increased from 60 to 90 mins (or longer depending upon total laminate thickness) at 135°C (275 °F) for large multi-ply laminates.
8. The interlayer should be removed from the holes after autoclaving with a core drill and then trimmed flush using an *exacto* or hot knife. Use of a torch is not recommended.

# Compatibility of SentryGlas Xtra® with coated glass or frits

Typically, SentryGlas Xtra® has very good adhesion to coated glass or ceramic frits. Contact your Kuraray account manager for an updated list of coatings that have been evaluated or check our website:

[www.trosifol.com](http://www.trosifol.com)

It is recommended that any low-e coating or frit not on the list be tested for adhesion and compatibility.

# Non-autoclave processing

Since SentryGlas Xtra® does not contain a plasticizer and has a very low as made moisture it is more easily laminated without trapped air defects than other interlayers using a non-autoclave process. Due to the increasing number and type of non-autoclave laminating lines that are now avail-

able specifying the proper conditions for each in this guide is not practical. Contact your Kuraray technical representative for assistance in optimizing non-autoclave process parameters to produce defect free laminates while minimizing process time.

# Quality assurance testing

It is strongly recommended that routine Quality Assurance (QA) testing be conducted. Testing should include, as a minimum, measurements of pummel adhesion and optical properties such as haze and transmission. SentryGlas Xtra® interlayer pummel adhesion measurements are done at room temperature (nominally 70°F/21°C) using PVB standards. Figure 38 shows a series of pummelled laminates with SentryGlas Xtra® with a range of adhesion from poor (1-2 pummels) to excellent (8 pummel).

Haze and transmission measurements should be made using a haze meter or direct comparison using visual standards.

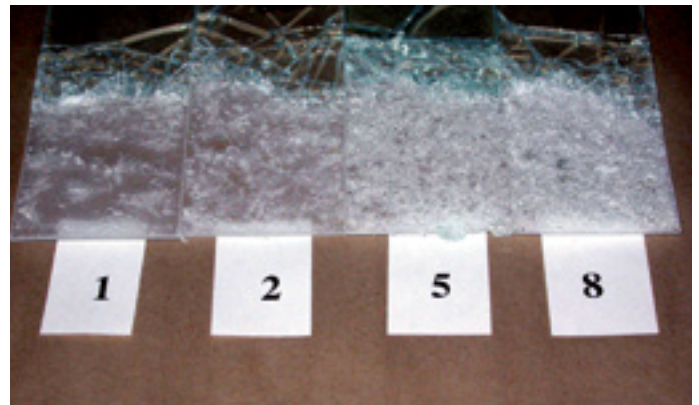


FIG 38 • Series of pummel measurements for different adhesion ranges

# Performance monitoring testing

All customers are strongly encouraged to submit samples with SentryGlas Xtra® for testing to Kuraray on a regular basis for Performance Monitoring (PM) Testing. Kuraray will measure glass construction, pummel adhesion, haze, caliper and interlayer moisture. The results are sent to the customer to monitor quality as a function of time.

## THE FOLLOWING ARE THE RECOMMENDED PM SUBMISSION GUIDELINES:

1. One laminate should be submitted with a TATA construction using 6 mm annealed glass. However, since the number of laminates and the frequency of submissions may vary by location please consult your Kuraray account manager or technical representative for more information.
2. Include the SentryGlas Xtra® lot number and the lamination date on the label.
3. If available include the laminator's QA test results.

# Troubleshooting

## Troubleshooting guide

| Problem      | Potential cause  | Solution  |
|--------------|--|---|
| Low adhesion | High moisture in sheeting.   | Use low moisture sheeting and check storage and handling methods.   |
| Low adhesion | Interlayer not getting to required temp for the required time.   | Check autoclave soak time and temperature. Ensure adequate spacing and good airflow. Increase soak time if needed. Use an internal thermocouple within the laminate to verify proper control. |
| Low adhesion | Incorrect pummel testing.  | Ensure the pummel test is done at room temperature.   |
| Trapped air  | Premature edge seal (most noticeable in trailing edge and does not extend to laminate edge).                             | Increase belt speed or lower furnace temperature.   |
| Trapped air  | Trapped air is randomly distributed in small areas due to excessive line (> 15 ft/min) speed (rolling over air pockets). | Decrease belt speed (may require lowering furnace temperature).   |
| Trapped air  | Roller nip gap too wide.   | Nip gap needs to be a minimum 0.1" less than the total laminate thickness.  |
| Trapped air  | Insufficient edge seal (autoclave "blow-in")<br>Trapped air extends to laminate edge(s).                                 | Decrease belt speed or raise furnace temperature.   |
| Trapped air  | Unequal heating causes air pockets to form on side of the interlayer.  | Adjust top and bottom furnace heaters so that the temperatures are equal.   |
| Trapped air  | Lines of air pockets are routinely distributed across the laminate due to roller wave distortion or excessive bowing.    | Check glass heat strengthening/tempering process. Nest laminates to reduce bowing.  |
| Iridescence  | Laminate has high stress areas during autoclaving.   | Eliminate any uneven stresses on the laminate and ensure the proper laminate separators are used.   |
| High haze    | Autoclave cooling rate too slow or non-uniform.  | Ensure cooling rate is at least 2°F/min (1°C/min) with good unobstructed airflow.   |

TAB 4

# Additional information

If there are questions regarding lamination of SentryGlas Xtra® for processing requests that fall outside of this laminating guide, please contact your Kuraray representative. Product safety information is available upon request. It is the user's responsibility to determine the level of risk and the proper protective equipment needed for the user's particular purposes.

The information provided herein corresponds to our knowledge on the subject of the date of its publication. This information may be subject to revision as new knowledge and experience becomes available. The data provided falls within the normal range of product properties and relate only to the specific material designated; this data may not be valid

for such material used in combination with any other materials or additives or in any process, unless expressly indicated otherwise. The data provided should not be used to establish specification limits or used alone as the basis of design; they are not intended to substitute for any testing you may need to conduct to determine for yourself the suitability of a specific material for your particular purposes.

Since Kuraray cannot anticipate all variations in actual end use conditions, Kuraray does not assume or undertake to discharge any responsibility in connection with any use of this information. Nothing in this publication is to be considered as a license to operate under a recommendation to infringe any patent rights.

# Tools & Apps

## WINSLT


For calculating the light, solar and heat parameters of glazing specifically containing films from the Trosifol® & SentryGlas® product range.

## SOUNDLAB AI

First global acoustic calculator based on artificial intelligence for calculating/estimating acoustic performance of monolithic, double and triple glazed units.

## SOLUTION FINDER

For finding the right product of your project.



## GLASGLOBAL

For performing structural analysis for glass.

## STRENGTH LAB AI

The goal of the Strength Lab AI tool is to provide designers, engineers, and architects with an efficient tool to facilitate the design and evaluation of glazing systems in terms of structural properties. This tool provides rapid analysis of virtually any glazing configuration, dimension and load case. Additionally, standard modules allow easy evaluation of results according to ASTM, EN and DIN standards.

\* Only available as web app



# Contact



## FOR FURTHER INFORMATION

on products from Kuraray, please visit [www.kuraray.com](http://www.kuraray.com).

You can find further information on our Trosifol® and SentryGlas® products at [www.trosifol.com](http://www.trosifol.com).

### Kuraray America, Inc.

Advanced Interlayer Solutions Division  
3700 Bay Area Boulevard  
Suite 680  
Houston, TX 77058, USA  
P +1 800 635 3182

[trosifol@kuraray.com](mailto:trosifol@kuraray.com)

### Kuraray Europe GmbH

Advanced Interlayer Solutions Division  
Kronenstr. 55  
53840 Troisdorf  
Germany  
P +49 2241 2555 226

### Kuraray Co., Ltd

Advanced Interlayer Solutions Division  
Tokiwabashi Tower  
2-6-4 Otemachi, Chiyoda-ku  
Tokyo 100-0004, Japan  
P +813 6701 1508

9/2024

Copyright © 2024 Kuraray. All rights reserved.

Trosifol, SentryGlas, SG, SentryGlas Xtra, SGX, BirdSecure, CamViera, SkyViera and Spallshield are trademarks or registered trademarks of Kuraray Co., Ltd. or its affiliates. Trademarks may not be applied for or registered in all countries. The information, recommendations and details given in this document have been compiled with care and to our best knowledge and belief. They do not entail an assurance of properties above and beyond the product specification. Final determination of suitability of any material or process and whether there is any infringement of patents is the sole responsibility of the user.

## **WORLD OF INTERLAYERS**

**What is the next project  
you are dreaming of?**

**[trosifol@kuraray.com](mailto:trosifol@kuraray.com)  
[www.trosifol.com](http://www.trosifol.com)**

